



Barium Titanate Nanoparticles Exhibit Cytocompatibility in Cultured Bovine Fibroblasts: A Model for Dermal Exposure

**Geovana de Carvalho Onorato ^a,
Danielle Luciana Aurora Soares do Amaral ^a,
Luiz Fernando Cappa de Oliveira ^b,
Humberto de Mello Brandao ^c and Michele Munk ^{a*}**

^a Department of Biology, Federal University of Juiz de Fora, Juiz de Fora, Minas Gerais, Brazil.

^b Department of Chemical, Federal University of Juiz de Fora, Nucleus of Spectroscopy and Molecular Structure, Juiz de Fora, Minas Gerais, Brazil.

^c Brazilian Agricultural Research Corporation, Laboratory of Applied Nanotechnology for Animal Production and Health, Brazilian Agricultural Research Corporation, Juiz de Fora, Minas Gerais, Brazil.

Authors' contributions

This work was carried out in collaboration among all authors. Authors MM and HdMB directed and designed the research study. Author DLASdA characterized the nanomaterials. Author GdCO conducted the In vitro evaluation of the cytotoxic and the statistical analysis. Authors MM and GdCO contributed to writing the manuscript. All authors read and approved the final manuscript.

Article Information

DOI: 10.9734/CJAST/2024/v43i54372

Open Peer Review History:

This journal follows the Advanced Open Peer Review policy. Identity of the Reviewers, Editor(s) and additional Reviewers, peer review comments, different versions of the manuscript, comments of the editors, etc are available here: <https://www.sdiarticle5.com/review-history/115461>

Original Research Article

Received: 07/02/2024

Accepted: 09/04/2024

Published: 12/04/2024

*Corresponding author: E-mail: michele.munk@ufjf.br;

ABSTRACT

The emergence of barium titanate nanoparticles (BaTiO₃ NPs) represents an advancement in various fields such as technology, health, and agribusiness. However, increased production heightens the risk of their dispersion into the environment, thereby raising concerns about potential exposure to animals and humans, including the risk of dermal exposure. This study explores the chemical-physical properties of BaTiO₃ NPs and their cytocompatibility using a bovine fibroblast cell model. The size and Zeta potential of the NPs were analyzed using scanning electron microscopy and dynamic light scattering technique. Raman spectroscopy was used to characterize the composition of the BaTiO₃ NPs. Bovine fibroblasts were exposed *in vitro* to NPs (0.1 to 100 µg mL⁻¹) for 24 hours to evaluate the cytocompatibility using the Thiazolyl Blue Tetrazolium Bromide assay and Trypan Blue exclusion test. The data were evaluated by analysis of variance and the means compared by the Tukey test. Scanning electron microscopy revealed that BaTiO₃ NPs measured approximately 100 nm. Dynamic light scattering analysis indicated a hydrodynamic size of 149.27 nm with a polydispersion index of 0.37, and the Zeta potential was -13mV. Raman spectroscopy analysis highlighted the cubic phase of BaTiO₃ NPs. Cytotoxicity tests demonstrated that BaTiO₃ NPs did not affect cell viability, with 10 µg mL⁻¹ resulting in enhanced cell proliferation. Overall, these findings underscore the non-toxic characteristics of BaTiO₃ NPs in fibroblast cells, positioning them as promising and cytocompatible nanomaterials.

Keywords: Ceramic nanomaterial; *In vitro* models; piezoelectricity; safe nanomaterials.

1. INTRODUCTION

Nanotechnology involves the manipulation of matter at atomic, molecular, and supramolecular levels to create novel materials, devices, and systems with unique properties and functionalities. With promising solutions across diverse domains, case studies abound, highlighting how nanoscale materials hold the potential to address contemporary challenges within the biomedical and agribusiness sectors [1,2]. The distinct ability to manipulate materials at the nanoscale makes nanotechnology unparalleled. On this scale, the forces governing matter differ significantly from those at the micro or macro scale [3]. Nanomaterials possess a defining characteristic: at least one dimension (height, width, or depth) measures less than 100 nanometers (nm), or 10⁻⁹ meters [4]. Consequently, nanomaterials exhibit unique physical and chemical properties, including significantly increased surface area and heightened reactivity compared to larger-scale materials [5].

Barium titanate nanoparticles (BaTiO₃ NPs) are perovskite bioceramic materials and have been considered emerging nanomaterials due to their ferroelectricity and piezoelectric properties [3,6]. Notably, recent reports suggest that BaTiO₃ NPs could be used in a wide range of applications including imaging diagnostics [7,8,] neural stimulation networks [9], drug nanocarriers [10], tissue engineering [11,12], and agribusiness [13].

The increasing concern over the toxicity of BaTiO₃ NPs arises from their vast range of potential applications, given that the rapid spread of these nanomaterials could potentially impact both animal and human health. Previous studies have demonstrated that toxicological risks are related to the fact of substantial differences in the chemical and physical properties of nanoscale materials compared to the same materials in bulk form [14,15]. Current research on the *in vitro* cytotoxicity of BaTiO₃ NPs in biological models is restricted. Especially, these studies incorporated BaTiO₃ NPs alongside other materials, potentially mitigating toxicity factors through functionalization [16-18].

Exposure of the skin to nanomaterials poses potential risks that require thorough understanding and mitigation [19]. Nanomaterials have the capability to penetrate the skin barrier and interact with underlying cells, potentially causing adverse effects such as cellular damage [20]. In this context, there is a gap regarding the possible toxic effects of skin exposure to BaTiO₃ NPs. Therefore, it is important to investigate the effects of nanomaterial exposure on skin cells using appropriate models. *In vitro* models utilizing cultured fibroblasts offer a valuable tool for studying cutaneous exposure to nanomaterials. Fibroblasts are a type of skin cell found in the dermis and play a crucial role in maintaining skin structure and function [21]. This *in vitro* cellular model allows for the study of cytotoxic mechanisms, encompassing changes

in cell morphology, alterations in metabolism, and cell death, in response to exposure to materials [22,23]. Therefore, the present work aimed to study the chemical-physical characteristics of BaTiO₃ NPs and their cytocompatibility with bovine fibroblast cells model cultured *in vitro*.

2. MATERIALS AND METHODS

2.1 Materials

BaTiO₃ NP (Product Number 467634, CAS Number 12047-27-7, purity > 99%, density of ~6,08 g/cm³), Dulbecco's Modified Eagle Medium (DMEM), fetal bovine serum (FBS), penicillin-streptomycin antibiotics, HCl and 3-(4,5-dimethylthiazol-2-yl)-2,5-diphenyltetrazolium bromide) thiazolyl blue tetrazolium bromide (MTT) assay kit were purchased from Sigma-Aldrich (St. Louis, MO, USA). Trypan Blue was purchased from Invitrogen (Carlsbad, CA, USA).

2.2 Dynamic Light Scattering Analysis

BaTiO₃ NP suspensions (100 µg mL⁻¹) were dispersed in DMEM medium by sonication using an ultrasonic instrument for 1 minute (cycle 0.5, amplitude 70) (UP200S, Hielscher, Teltow, Germany). The average size and Zeta potential were determined using the dynamic light scattering (DLS) technique with the Malvern 3000 Zetasizer NanoZS equipment (Malvern Instruments, UK).

2.3 Scanning Electron Microscopy (SEM)

The size distribution and morphology of BaTiO₃ NPs were characterized through scanning electron microscopy (SEM) analysis. This analysis was conducted using a high-resolution Zeiss-DSM 950 microscope (manufactured by Zeiss, Germany) operating at an accelerating voltage of 6 kilovolts (kV).

2.4 Raman Spectroscopy

Raman Spectroscopy was performed with a Bruker RFS 100 (Bruker, USA) spectrometer excited with a Nd + 3/YAG laser operating at 1064 nm, equipped with an InGaAs detector cooled with liquid nitrogen. The spectra were acquired at 4 cm⁻¹ resolution. An average of 1024 scans were collected with a laser power rating of 110 mW.

2.5 Cell Culture

Primary fibroblast cell cultures derived from bovine skin biopsies were stored in the cell bank

of the Brazilian Agricultural Research Corporation. All relevant biosafety regulations were strictly followed, following the approved procedures of the Internal Biosafety Commission under protocol number 03/2012. To establish the cell bank, fibroblasts from the skin biopsies were cultured in DMEM supplemented with 10% FBS and 100 units/ml of penicillin-streptomycin. The cells were incubated at 37°C, 5% CO₂, and 95% humidity (Model 4130, Thermo Fisher Scientific, Waltham, MA, USA), and cryopreserved after the second passage. Before their use in this study, fibroblasts were thawed and subsequently cultured up to the third passage.

2.6 *In vitro* Nanoparticle Exposure

In vitro cytotoxicity assays were based on ISO 10993-5 [24]. Samples of BaTiO₃ NPs at a concentration of 5 mg mL⁻¹ were dispersed in DMEM cell culture medium, supplemented with 10% FBS. Then, fibroblast cells (60% confluence) were seeded into 96-well plates at a 6x10³ cells/well. Cells were incubated with BaTiO₃ NPs at different concentrations: 0 (vehicle control), 0.1, 1, 10, 50, and 100 µg mL⁻¹ for 24 hours.

2.7 Cell Morphology Analysis

Monitoring the growth and cell morphology of fibroblasts was performed using light microscopy (Nikon TS100F, Nikon Instruments Inc., Melville, NY, USA) to evaluate the possible impact of cell exposure to BaTiO₃ NPs on cell morphology.

2.8 Mitochondrial Metabolism Assay

Cell proliferation was evaluated after exposure of cells to different experimental groups by the Thiazolyl Blue Tetrazolium Bromide assay (MTT), which assesses mitochondrial activity. After NP exposure, MTT aliquots at the concentration of 5 mg mL⁻¹ were prepared, and then incubated with the cell cultures using this solution in the culture medium, for 4 hours at 37°C, in a humidified atmosphere containing 5% CO₂ and 95% atmospheric air. After the culture medium was removed and isopropanol-acid 0.04 M HCl was added to complete the solubilization of the precipitate. Then, the absorbance was determined using the wavelength of 570 nm in the Eon Microplate Reader equipment (BioTek, Winooski, USA). Cell viability results in the groups exposed to BaTiO₃ NP were expressed as a percentage compared with the control group.

2.9 Trypan Blue Assay

The trypan blue exclusion test assessed the effect of BaTiO₃ NP on cell viability [23]. After NP exposure, the cells were trypsinized and stained with 0.4% Trypan Blue solution. Then, the cells were counted using a hemocytometer.

2.10 Statistical Analysis

Data from the cell viability assay were evaluated by variance analysis (ANOVA) and the means were compared by the Tukey test. P values lower than 0.05 were considered significant. The results were presented as means \pm standard error (EP) of the mean.

3. RESULTS AND DISCUSSION

Initially, we carried out the physicochemical characterization of the BaTiO₃ NPs to gain deeper insights into their inherent properties. The hydrodynamic size of the BaTiO₃ NPs was measured at 149.27 \pm 0.81 nm, with a polydispersion index of 0.37. Furthermore, the suspension of BaTiO₃ NPs displayed a Zeta potential of -15.3 \pm 0.78 mV. The dispersion status of nanomaterials can significantly influence their impact on biological systems [25]. A polydispersion index of 0.37 characterizes a moderately polydisperse sample [26], suggesting a potential instability of the BaTiO₃ NP suspension. Zeta potential, also known as electrokinetic potential, serves as an indicator of dispersion stability and is a crucial factor

influencing the interaction of nanomaterials with cellular components. Generally, values exceeding 30 mV (in modulus) for particulate matter are deemed stable due to electrostatic repulsion [27]. Instabilities in the suspension may result in the formation of clusters consisting of weakly linked nanomaterials, or aggregates comprising strongly bonded nanomaterials that are challenging to separate. These occurrences are common when the Zeta potential falls below 20 mV [28].

The morphological assessment of the BaTiO₃ NP suspensions obtained via SEM revealed the presence of aggregates (Fig. 1), with the nanoparticles appearing to be approximately 100 nm in size.

The size of the nanomaterial is a critical determinant of its toxicity, which is essential for any biotechnological application [29]. Nanomaterial size can affect their penetration into cells, tissues, and organs, as well as their increased interaction with specific membrane receptors, facilitated by their highly reactive nature due to free atoms on their extensive surface area [30]. This diminutive nanomaterial size can induce oxidative stress, DNA damage, and cell death [4,31-33]. In this investigation, the moderate polydisperse sample of BaTiO₃ NPs exhibited an average size of 149.27 \pm 0.81 nm, indicating a dispersion comprising small particle sizes and a limited number of aggregates, as observed in the SEM image (Fig. 1B), likely attributable to the low modulus value of the Zeta potential.

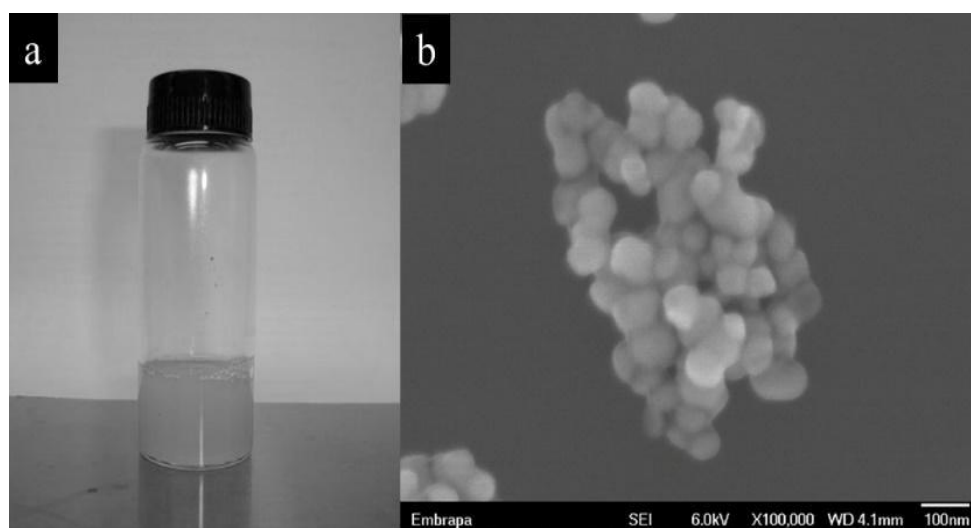


Fig. 1. (a) Suspensions of barium titanate nanoparticles (BaTiO₃ NPs) in Dulbecco's Modified Eagle Medium (100 μ g mL⁻¹). (b) Scanning electron microscopy (SEM) images of BaTiO₃ NPs. Scale bar =100 nm

Raman spectroscopy was used to examine the structure of BaTiO₃ NPs. Raman peaks of BaTiO₃ NPs located at 192 cm⁻¹, 306 cm⁻¹, 511 cm⁻¹, 716 cm⁻¹ assigned at [A₁(TO), E(LO)]; (B₁, E(TO + LO)); (A₁(TO), E(TO)) and (A₁(LO), E(LO)), respectively (Fig. 2). In Raman measurements, the characteristic feature of the tetragonal BaTiO₃ NPs phase is observed around 306 cm⁻¹. The broad band at 513 cm⁻¹ can be attributed to the intrinsic cubic phase (Fig. 2), corroborating data available in the literature that characterizes these nanomaterials with cubic and tetragonal formats [34-37].

Cells were exposed to different concentrations (0.1-100 µg mL⁻¹) of BaTiO₃ NPs for 24, 48 h, and cell viability was measured by microscopy analyses, MTT and Trypan Blue assays. The evaluation of cellular morphology is a critical parameter in nanotoxicity studies [38]. In our current study, we observed no significant changes in the cellular morphology of fibroblasts at any concentration of BaTiO₃ NPs compared to the control group (Fig. 3).

Similar findings were reported by Amaral et al. [12] who did not detect any changes in the morphology of human mesenchymal stem cells in vitro exposed to BaTiO₃ NPs. However, several nanomaterials induce cellular toxicity through the generation of reactive oxygen

species, which can impact the dynamics of microtubules, thereby modifying cell morphology [39,40]. Ahamed et al. [41] reported alterations in cell morphology among human lung carcinoma (A549) cells exposed to BaTiO₃ NPs, attributing these changes to oxidative stress. However, our investigation did not reveal any significant changes in cell morphology following exposure to BaTiO₃ NPs. One potential explanation could be attributed to the specific cellular model utilized, as exposure routes such as air and skin contact may induce distinct toxicological responses.

Importantly, aggregate points of the nanoparticles were evident at concentrations of 50 and 100 µg mL⁻¹, as depicted by the arrows (Fig. 3E, F). Despite studies in the literature demonstrating that nanoparticle aggregation induces nanotoxicity [42], our study showed that aggregation also did not induce cytotoxic responses. The presence of BaTiO₃ NPs aggregates might have been influenced by the composition of the culture medium containing fetal bovine serum proteins. Consequently, a future study could investigate the impact of varying concentrations of fetal bovine serum on BaTiO₃ NP toxicity.

Based on the MTT assay BaTiO₃ NPs, except for at 10 µg mL⁻¹, did not significantly impact cell proliferation when compared to the non-exposed control (P>0.05) (Fig. 4).

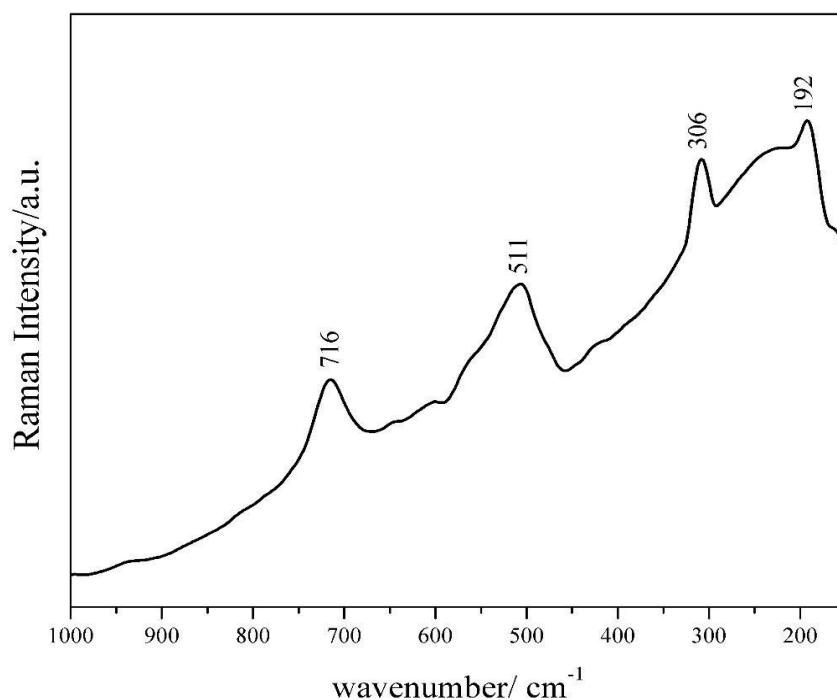


Fig. 2. Raman spectra of barium titanate nanoparticles (BaTiO₃ NPs)

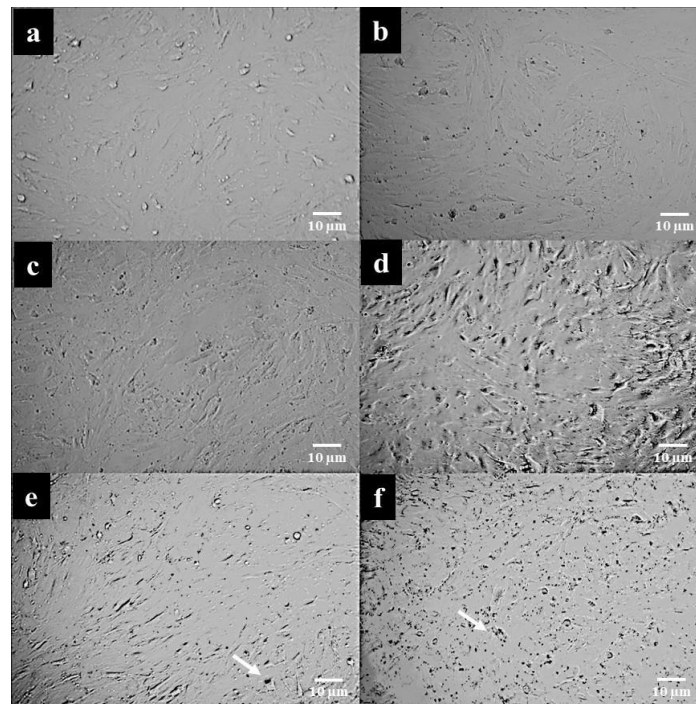


Fig. 3. Cellular morphology evaluation of bovine fibroblasts exposed to barium titanate nanoparticles (BaTiO₃ NPs) for 24 hours. (a) 0 (Control), (b) 0.1, (c) 1, (d) 10, (e) 50, and (f) 100 µg mL⁻¹. Magnification 100×. Scale bar = 10 µm

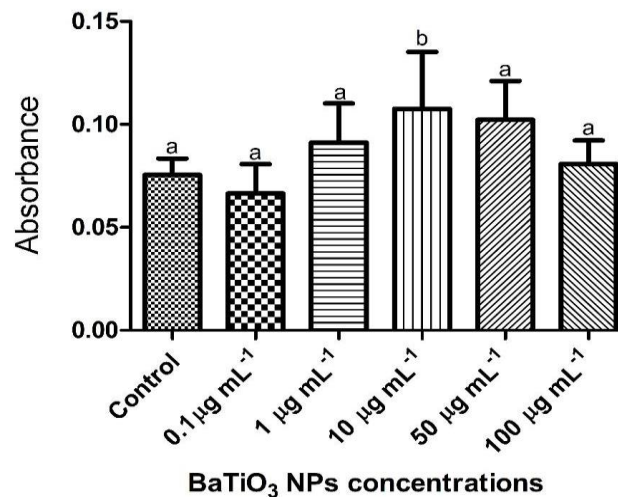


Fig. 4. Analysis of bovine fibroblast cell proliferation exposed to barium titanate nanoparticles (BaTiO₃ NPs) using the MTT assay. Mean percentage of viable cells after exposure to concentrations of 0 (control). 0.1, 1, 10, 50 e 100 µg mL⁻¹ of BaTiO₃ NPs for 24 hours. *P<0.05

Notably, the concentration of 10 µg mL⁻¹ BaTiO₃ NPs led to an increase in cell proliferation compared to the control group (P<0.05). The MTT assay, a common colorimetric test used to evaluate cell viability, operates by converting tetrazolium salt into formazan crystals through a

mitochondrial membrane, serving as an indicator of cell proliferation [43,44]. Several studies in nanotoxicology utilize this test as an initial parameter to assess the toxicity of nanomaterials [12,45-47]. In our study, the 10 µg mL⁻¹ concentration of BaTiO₃ NPs promoted cell

proliferation compared to the control group, consistent with previous research demonstrating enhanced adhesion and proliferation of human osteoblastic cells following exposure to BaTiO₃ NPs [48]. The increase in cell proliferation at a concentration of 10 µg mL⁻¹ might be attributed to the potential stimulation of specific cell signaling pathways or the facilitation of cellular metabolic activities, potentially leading to enhanced cell division. Additionally, this enhanced cell proliferation could be associated with the cytocompatibility of BaTiO₃ NPs at this specific concentration, indicating a favorable response of the cells to the nanoparticle stimulus.

On the other hand, the present study did not detect changes in cell proliferation at concentrations of 50 and 100 µg mL⁻¹. This finding is consistent with prior studies, which similarly showed no differences in the MTT test when human mesenchymal stem cells were exposed to BaTiO₃ NPs for 24 h, even at elevated concentrations [12]. These results are likely attributed to the observed increase in the formation of nanoparticle aggregates at concentrations of 50 and 100 µg mL⁻¹ BaTiO₃ NPs, thereby reducing the availability of free nanoparticles for interaction with cells.

A Trypan Blue test was conducted to investigate the cell viability of fibroblast cells cultured with BaTiO₃ NPs (Fig. 5). This assay relies on the

principle that cells with intact membranes exclude Trypan blue dye [21]. The results demonstrated that none of the BaTiO₃ NP treatments significantly altered cell viability when compared to the control group (P>0.05).

Similarly, a previous study reported no decrease in cell viability in vitro when stem cells were exposed to BaTiO₃ NPs at the same concentrations as in our study [12]. However, another study has demonstrated that the cell viability of A549 cells exposed to concentrations of up to 50 µg mL⁻¹ BaTiO₃ NPs for 24 h was reduced [41]. The differing responses observed in these studies may be attributed to the specific cell lineage under evaluation. It is plausible that the physiological characteristics of the fibroblast cells, including their innate resistance to external stressors and their capacity to adapt to various environmental conditions, played a role in maintaining cell viability despite exposure to BaTiO₃ NPs. Moreover, the intricate interplay between the physicochemical properties of the BaTiO₃ NPs and the cellular microenvironment could have influenced the cells' response. This includes parameters such as the surface charge, size, and aggregation status of the nanoparticles, as well as the composition of the cell culture medium and the presence of serum components, which might have interacted with the nanoparticles, thereby influencing their overall cytocompatibility.

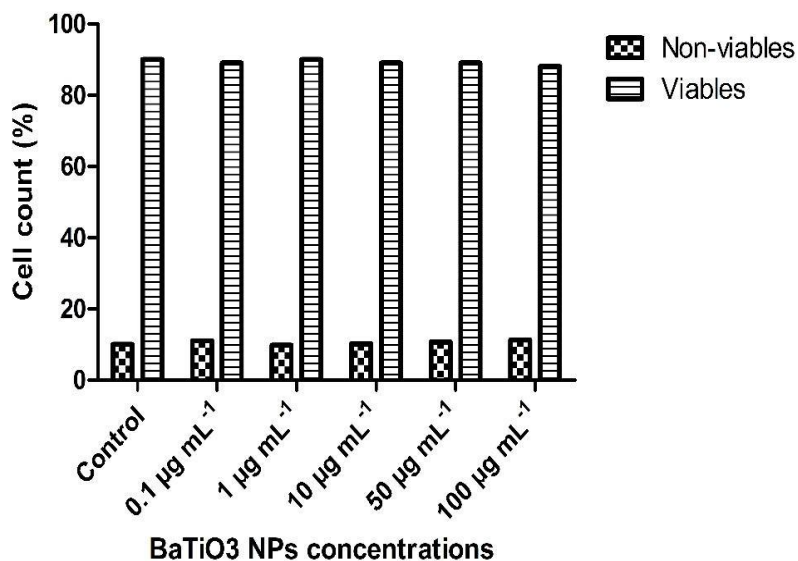


Fig. 5. Analysis of bovine fibroblast cellular viability exposed to barium titanate nanoparticles (BaTiO₃ NPs) using the Trypan Blue Assay. Mean percentage of viable cells after exposure to concentrations of 0 (control). 0.1, 1, 10, 50 e 100 µg mL⁻¹ of BaTiO₃ NPs for 24 hours

4. CONCLUSION

Under the experimental conditions of this study, BaTiO₃ NPs exhibited cytocompatibility with bovine fibroblasts, with a notable observation that at a concentration of 10 µg mL⁻¹, BaTiO₃ NPs led to increased cell proliferation. These findings provide valuable insights into the safety profile of BaTiO₃ NPs, particularly in their potential applications within the medical and agricultural industries.

ETHICAL APPROVAL

All authors hereby declare that "Principles of laboratory animal care" (NIH publication No. 85-23, revised 1985) were followed, as well as specific national laws where applicable. All experiments have been examined and approved by the appropriate ethics committee.

ACKNOWLEDGEMENTS

This research was funded by This work was supported by the National Council for Scientific and Technological Development (CNPq) [grant number 303148/2021-7], and the Minas Gerais State Research Support Foundation (FAPEMIG) [grant number APQ-01855-23, RED00081-23 and PPM 00691/17]. The authors would like to thank the National Network of Alternative Methods (RENAMA), the Coordination for the Improvement of Higher Education Personnel (CAPES), the Integrated Research Laboratory (LIP) and the Graduate Program in Biological Sciences (PPGC BIO/UFJF).

COMPETING INTERESTS

Authors have declared that no competing interests exist.

REFERENCES

1. Nanotechnology Products Database; 2023. Available: <https://product.statnano.com>. Accessed in November 2023.
2. Harish V, Tewari D, Gaur M, et al. Review on nanoparticles and nanostructured materials: bioimaging, biosensing, drug delivery, tissue engineering, antimicrobial, and agro-food applications. *Nanomaterials* (Basel). 2022;12(3):457.
3. Kareem YM, Hamad TI. Assessment of the antibacterial effect of *Barium titanate* nanoparticles against *Staphylococcus* epidermidis adhesion after addition to maxillofacial silicone. *F1000Research*. 2023;12:385.
4. Akçan R, Aydoğan HC, Yildirim MŞ, et al. Nanotoxicity: A challenge for future medicine. *Turkish Journal of Medical Sciences*. 2020;50(4):1180-96.
5. Kargozar S, Mozafari M. Nanotechnology and nanomedicine: Start small, think big. *Materials Today: Proceedings*. 2018;5(7):15492-500.
6. Choi I, Lee SJ, Kim JC, et al. Piezoelectricity of picosecond laser-synthesized perovskite BaTiO₃ nanoparticles. *Applied Surface Science*. 2020;511:145614.
7. Marino A, Almici E, Migliorin S, et al. Piezoelectric barium titanate nanostimulators for the treatment of *Glioblastoma multiforme*. *Journal of Colloid and Interface Science*. 2019;538:449-61.
8. Yoon YN, Lee DS, Park HJ, et al. Barium titanate nanoparticles sensitise treatment-resistant breast cancer cells to the antitumor action of tumour-treating fields. *Scientific Reports*. 2020;10(1):2560.
9. Rojas C, Tedesco M, Massobrio P, et al. Acoustic stimulation can induce a selective neural network response mediated by piezoelectric nanoparticles. *Journal of Neural Engineering*. 2018;15(3):036016.
10. Sood A, Desseigne M, Dev A, et al. A Comprehensive Review on Barium Titanate Nanoparticles as a Persuasive Piezoelectric Material for Biomedical Applications: Prospects and Challenges. *Small*. 2023;19(12):e2206401.
11. Zheng Y, Zhao L, Li Y, et al. Nanostructure Mediated Piezoelectric Effect of Tetragonal BaTiO₃ Coatings on Bone Mesenchymal Stem Cell Shape and Osteogenic Differentiation. *International Journal of Molecular Sciences*. 2023;24(4):4051.
12. Amaral DL, Zanette RS, Almeida CG, et al. In vitro evaluation of barium titanate nanoparticle/alginate 3D scaffold for osteogenic human stem cell differentiation. *Biomedical Materials* (Bristol, England). 2019;14(3):035011.
13. El-Sayed A, Kamel M. Advanced applications of nanotechnology in veterinary medicine. *Environmental Science and Pollution Research International*. 2020;27(16):19073-86.
14. Hussain Z, Thu HE, Haider M, et al. A review of imperative concerns against clinical translation of nanomaterials:

- unwanted biological interactions of nanomaterials cause serious nanotoxicity. *Journal of Drug Delivery Science Technology*. 2020;59:101867.
15. Yao Y, Zhang T, Tang M. Toxicity mechanism of engineered nanomaterials: Focus on mitochondria. *Environmental Pollution*. 2024;343:123231.
 16. Dubey AK, Thrivikraman G, Basu B. Absence of systemic toxicity in mouse model towards BaTiO₃ nanoparticulate based eluate treatment. *Journal of Materials Science. Materials in Medicine*. 2015;26(2):103.
 17. Abdelkhalik A, van der Zande M, Punt A, et al. Impact of nanoparticle surface functionalization on the protein corona and cellular adhesion, uptake and transport. *Journal of Nanobiotechnology*. 2018;16(1):70.
 18. Popescu RC, Andronescu E, Vasile BS. Recent advances in magnetite nanoparticle functionalization for nanomedicine. *Nanomaterials (Basel, Switzerland)*. 2019;9(12):1791.
 19. Gimeno-Benito I, Giusti A, Dekkers S, et al. A review to support the derivation of a worst-case dermal penetration value for nanoparticles. *Regulatory Toxicology and Pharmacology*. 2021;119:104836.
 20. Hashempour S, Ghanbarzadeh S, Maibach HI, et al. Skin toxicity of topically applied nanoparticles. *Therapeutic Delivery*. 2019;10(6):383-96.
 21. Pliikus MV, Wang X, Sinha S, et al. Fibroblasts: Origins, definitions, and functions in health and disease. *Cell*. 2021;184(15):3852-72.
 22. Atsu PM, Mowen C, Thompson GL. Enhanced cell viability and migration of primary bovine annular fibrosus fibroblast-like cells induced by microsecond pulsed electric field exposure. *ACS Omega*. 2023;8(40):36815-22.
 23. Defendi-Cho G, Gould TM. In vitro culture of bovine fibroblasts using select serum-free media supplemented with *Chlorella vulgaris* extract. *BMC Biotechnology*. 2023; 23:4.
 24. ISO Guide 10993-5:2009: Biological evaluation of medical devices—Part 5: Tests for in vitro cytotoxicity, ISO: Geneva, 2009.
 25. Roy S, Aastha, Deo KA, et al. Nanobio Interface Between Proteins and 2D Nanomaterials. *ACS Applied Materials & Interfaces*. 2023;15(30):35753-35787.
 26. Abdel-Rahman MA, Alshallash KS, Eid AM, et al. Exploring the Antimicrobial, Antioxidant, and Antiviral Potential of Eco-Friendly Synthesized Silver Nanoparticles Using Leaf Aqueous Extract of *Portulaca oleracea* L. *Pharmaceuticals (Basel)*. 2024;17(3):317.
 27. ISO Guide 22412:2017: Particle size analysis – dynamic light scattering (DLS), ISO: Geneva, 2017.
 28. Anand K, Siby V, Thomas K. Effect of ball size on milling efficiency of zinc oxide dispersions. *Particulate Science and Technology*. 2018;36(2):308-11.
 29. Shrestha S, Wang B, Dutta P. Nanoparticle processing: understanding and controlling aggregation. *Advances in Colloid and Interface Science*. 2020;279:102162.
 30. Fu X, Cai J, Zhang X, et al. Top-down fabrication of shape-controlled, monodisperse nanoparticles for biomedical applications. *Advanced Drug Delivery Reviews*. 2018;132:169-87.
 31. Singh S. Zinc oxide nanoparticles impacts: Cytotoxicity, genotoxicity, developmental toxicity, and neurotoxicity. *Toxicology Mechanisms and Methods*. 2019;29(4):300-11.
 32. Fayer L, Zanette RS, Siqueira JTC, et al. The distinct effect of titanium dioxide nanoparticles in primary and immortalized cell lines. *Toxicology Research*. 2021;10(3):511-22.
 33. Huang C, Wu D, Khan FA, et al. Zinc oxide nanoparticle causes toxicity to the development of mouse oocyte and early embryo. *Toxicology Letters*. 2022;358:48-58.
 34. Ciofani G, Danti S, Moscato S, et al. Preparation of stable dispersion of barium titanate nanoparticles: Potential applications in biomedicine. *Colloids and surfaces. B, Biointerfaces*. 2010;76(2):535-43
 35. Ciofani G, Ricotti L, Mattoli V. Preparation, characterization and in vitro testing of poly(lactic-co-glycolic) acid/barium titanate nanoparticle composites for enhanced cellular proliferation. *Biomedical Microdevices*. 2011;13(2):255-66.
 36. Hayashi H, Nakamura T, Ebina T. In-situ Raman spectroscopy of BaTiO₃ particles for tetragonal–cubic transformation. *Journal of Physics and Chemistry of Solids*. 2013;74(7):957-62.
 37. Kim Y, Kim H, Oh HT, et al. Highly fluorinated barium titanate nanoparticle

- dispersion for fabrication of lithographically patterned thin films. *Materials* (Basel, Switzerland). 2019;12(24):4045.
38. Li J, Ning M, Zhang Y, et al. The potential for nanomaterial toxicity affecting the male reproductive system. *Wiley Interdisciplinary Reviews: Nanomedicine and Nanobiotechnology*. 2022;14(6): e1806.
 39. de Souza W, Gemini-Piperni S, Grenho L, et al. Titanium dioxide nanoparticles affect osteoblast-derived exosome cargos and impair osteogenic differentiation of human mesenchymal stem cells. *Biomaterials Science*. 2023;11(7):2427-2444.
 40. Ma X, Hartmann R, Jimenez de Aberasturi D, et al. Colloidal gold nanoparticles induce changes in cellular and subcellular Morphology. *ACS Nano*. 2017;11(8):7807-20.
 41. Ahamed M, Akhtar MJ, Khan MAM, et al. Barium Titanate (BaTiO₃) nanoparticles exert cytotoxicity through oxidative stress in human lung carcinoma (a549) cells. *Nanomaterials* (Basel). 2020;10(11):2309.
 42. Murugadoss S, Brassinne F, Sebaihi N, et al. Agglomeration of titanium dioxide nanoparticles increases toxicological responses in vitro and in vivo. *Particle and Fibre Toxicology*. 2020;17(1):10.
 43. Coyle JP, Johnson C, Jensen J, et al. Variation in pentose phosphate pathway-associated metabolism dictates cytotoxicity outcomes determined by tetrazolium reduction assays. *Scientific Reports*. 2023; 13(1):8220.
 44. Präbst K, Engelhardt H, Ringgeler S, Hübner H. Basic colorimetric proliferation assays: MTT, WST, and resazurin. *Methods in Molecular Biology* (Clifton, N.J.). 2017;1601:1-17.
 45. Braun K, Stürzel C. M., Biskupek J, Kaiser U, Kirchhoff F, Lindén M. Comparison of different cytotoxicity assays for in vitro evaluation of mesoporous silica nanoparticles. *Toxicology in Vitro*. 2018;52:214-21.
 46. Castellani S, Trapani A, Spagnoletta A, et al. Nanoparticle delivery of grape seed-derived proanthocyanidins to airway epithelial cells dampens oxidative stress and inflammation. *Journal of Translational Medicine*. 2018;16(1): 140.
 47. Dong L, Tang S, Deng F, et al. Shape-dependent toxicity of alumina nanoparticles in rat astrocytes. *The Science of the Total Environment*. 2019;690:158-66.
 48. Lyons JG, Plantz MA, Hsu WK, Hsu EL, Minardi S. Nanostructured biomaterials for bone regeneration. *Frontiers in Bioengineering and Biotechnology*. 2020; 8:922.

© Copyright (2024): Author(s). The licensee is the journal publisher. This is an Open Access article distributed under the terms of the Creative Commons Attribution License (<http://creativecommons.org/licenses/by/4.0>), which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited.

Peer-review history:

The peer review history for this paper can be accessed here:
<https://www.sdiarticle5.com/review-history/115461>